

# Jurnal\_Bacterial\_Characterizatio n\_of\_silver

*by* Yuherman Yuherman

---

**Submission date:** 22-Jun-2021 07:12PM (UTC+0800)

**Submission ID:** 1610580957

**File name:** Jurnal\_Bacterial\_Characterization\_of\_silver...pdf (2.35M)

**Word count:** 2795

**Character count:** 15746



## Research Article

### BACTERIAL CHARACTERIZATION OF SILVER NANOPARTICLES FROM TEMBAGAPURA SOIL SAMPLE ISOLATE, PAPUA, INDONESIA

Dani Prasetyo <sup>1,2</sup>, Muhammad Fadli <sup>1</sup>, Yuherman <sup>3</sup>, <sup>23</sup>ska Permata Dewi <sup>4</sup>, Akmal Djamaan <sup>5\*</sup>

<sup>1</sup>Department of Biotechnology, Graduate School of Andalas University, Padang, West Sumatera, Indonesia

<sup>2</sup>Faculty of Pharmacy, Kader Bangsa University, Palembang, South Sumatra, Indonesia

<sup>3</sup>Animal Husbandry Faculty, Andalas University, Padang, West Sumatera, Indonesia

<sup>4</sup>Department of Pharmacy, Faculty of Public Health, University of Abdurrab, Pekanbaru, Riau, Indonesia,

<sup>5</sup>Department of Pharmaceutical Chemistry, Faculty of Pharmacy, Andalas University, Padang, West Sumatera, Indonesia

\*Corresponding Author Email: akmaldjamaan@phar.unand.ac.id

Article Received on: 11/09/18 Approved for publication: 20/10/18

DOI: 10.7897/2230-8407.0910225

#### ABSTRACT

Characterization of silver nanoparticle-producing bacteria from Tembagapura, Papua, Indonesia soil samples isolates has been <sup>24</sup>stigated. Bacteria characterization was carried out macroscopically <sup>11</sup>, microscopically, biochemically and molecularly. Furthermore, the results of the formed silver nanoparticles were characterized using UV-VIS spectroscopy, Fourier transform infrared (FTIR) and scanning electron microscopy (SEM). The experimental results showed maximum absorbance at 414 nm in TP10-1 isolates in UV-Vis <sup>4</sup> spectroscopy. FTIR spectra of silver nanoparticles samples of TP10-1 isolates showed strong peaks in wave numbers 1637.65 cm<sup>-1</sup> and 3329.47 cm<sup>-1</sup>. SEM micrographs <sup>4</sup> reveal the formation of well dispersed silver nanoparticles. Silver nanoparticles of TP10-1 isolates that was measured by the imageJ program had an average particle size of 16,991 nm. Bacterial isolates with TP10-1 sample code which are identical to the Bacillus cereus strain GCF112 was able to synthesize silver nanoparticles.

**Keywords:** silver nanoparticle, characterization, *Bacillus cereus* strain GCF112

#### INTRODUCTION

Nanotechnology development is still developing by the researchers from academic world and from the industrial world. Nano particle synthesis means making particles with sizes less than 100 nm and at the same time changing their properties or functions<sup>1</sup>. One of the most popular nanoparticles is nanosilver particles or nanosilver particles (NSPs). If the particle size is <sup>5</sup>wered, the surface area with the NSPs volume ratio will increase dramatically, which leads to significant change <sup>5</sup> in physical, chemical, and biological aspect. NSPs are most commonly used in health care systems for hundreds of years<sup>2</sup>.

<sup>3</sup> Biosynthesis (green synthesis) of nanosilver has received widespread attention because of its growing need for environmentally friendly synthesis methods and the use of environmentally friendly reducing and capping agents, such as proteins, peptides, carbohydrates, from various species of bacteria, fungi, yeast and algae and plants<sup>2</sup>.

In this paper, we will be used to synthesize nanosilver particles (NSPs) from bacteria isolated from Tembaga Pura, Papua soil and reported the characterization was formed. Bacteria from Tembagapura which produce nanosilver will be identified molecularly.

#### MATERIAL AND METHOD

##### Isolation of Silver Nanoparticle-Producing Bacteria

Soil samples obtained from Tembagapura were used as a source for bacterial isolate. A total of 10 g of soil samples were put into 90 ml of NB medium, then incubated for 24 - 48 hours at 37 °C,

then it was diluted to 10<sup>3-4</sup>. Isolation of metal-resistant bacteria (Ag) was carried out by duplicate plating technique using a nutrient equipped with a 1 mM concentration of sterilized AgNO<sub>3</sub> and using NA medium only. Then it was incubated at 37 °C for 48-72 hours, the Petri dish was observed to determine the bacterial growth<sup>5,6</sup>. Cultures of growing isolates were identified as silver resistant bacteria. Separately grown bacterial colonies were then purified using the streak plate method on nutrient agar (NA) medium.

##### Conventional Identification of Bacteria

Conventional Identification Bacteria that produce silver nanoparticles were further identified by conventional methods. The main identification of bacterial isolates was carried out on the basis of colony, microscopic and biochemical characteristics which refer to the Bergey's Manual of Determinative of Microorganism<sup>3,7</sup>.

##### Molecular Identification of Silver Nanoparticles- Producing Bacteria

Molecular identification of bacterial isolates was done using the 16SrRNA gene. DNA products of bacterial <sup>14</sup> isolates from amplification and purification were sequenced by Macrogen Inc. (South Korea). Sequence data were analyzed using the BLAST program (www.ncbi.nlm.gov/blast) and phylogenetic trees was built<sup>8</sup>.

<sup>10</sup>

##### Extracellular Biosynthesis of Silver Nanoparticles

Extracellular synthesis of silver nanoparticles was carried out as described by Shahverdi et al. (2007) with a few modifications as

given below. Isolated colonies were cultured in NB and incubated for 24 hours at 37 °C. Then, NB was centrifuged at 8000 rpm for 10 minutes to collect the supernatant. Silver nitrate solution as 1 mM was prepared with distilled water. As much as 20 mL of 1 mM silver nitrate solution were mixed with 10 mL of the culture supernatant in a 50 mL Erlenmeyer flask. All samples were shaken using shaker tool at 150 rpm and maintained in dark conditions for 36-72 hours. Silver nitrate reduction was monitored with visible color changes from the solution<sup>5,9</sup>.

#### Synthesis Evaluation of Silver Nanoparticle

This synthesis evaluation of silver nanoparticle formed was done using UV-Vis spectrophotometer, Fourier transform infrared (FTIR) and Scanning Electron Microscopy (SEM)<sup>10,11,12</sup>.

### RESULTS AND DISCUSSION

#### Isolation of Silver Nanoparticles-Producing Bacteria

Pure colonies grown on nutrient agar (NA) medium which had been added with 1mM AgNO<sub>3</sub> solution were taken one of them and given isolate code TP10-1. These colonies are considered as resistant bacteria to silver solution, then characterization of the bacteria and the products of silver nanoparticles formed was done. Characterization of bacterial isolates obtained was done by comparing the isolate with standard literature. The result showed that the bacteria was Gram positive and has bacillary form (Fig. 1). Endospore tests were carried out on these isolates and showed that these bacteria can form endospores. Furthermore, biochemical tests were carried out, one of which was catalase test.

This test result showed that the bacterial isolates were positively catalase, characterized by the formation of bubbles. These results indicate that the isolate is likely to be Bacillus.

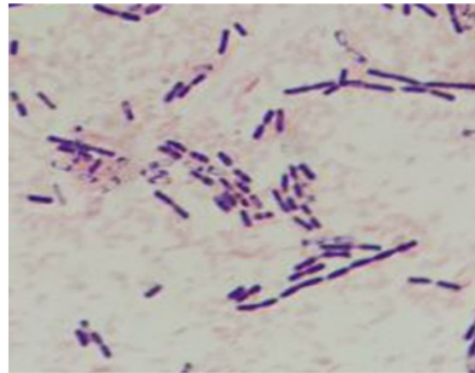


Figure 1: The results of Gram staining isolation of TP10-1 bacteria with 10x100 magnification

#### Molecular identification of silver nanoparticles-producing bacteria

The sequencing results of TP10-1 bacterial isolates were compared with GeneBank data using the BLAST program which was conducted online on the NCBI website.

```
>TP10-1
AGCTTGCTCTTATGAAGTTAGCGGCGGACGGGTGAGTAACACGTGGGTAACCTGCCATAAGACTGGGATAACTCCGG
GAAACCGGGCTAATACCGGATAACATTTTGAACGCATGGTTCGAAATTGAAAGCGGCTTCGGCTGTCACATTATGGA
TGGACCCCGCTGCATTAGCTAGTTGGTGAAGTAACGGCTCACCAGGCAACGATGCGTAGCCAACCTGAGAGGGTGAT
CGGCCACACTGGGACTGAGACACGGCCAGACTCCACGGGAGGACAGTAGGGAATCTTCCGCAATGGACGAAAGTC
TGACGGAGCAACGCCCTGGAGTGATGAAGCTTTCGGGTCGTAAGAACCTGTTGTTAGGGAAGAACAAGTGTAGTTG
AATAAGCTGGCACCTTACGGTACCTAACAGAAAGCCACGGCTAACCTACGTGCCAGCAGCCGCGGTAATACGTAGGTG
GCAAGCGTTATCCGGAATATTGGGCGTAAAGCGCGCAGGTGGTTTCTTAAGTCGTATGTGAAAGCCACGGCTCAA
CCGTGGAGGGTCATTGGAACTGGGAGACTTGAGTGCAGAAAGGAAAGTGGAAATCCATGTGTAGCGGTGAAATGCGT
AGAGATATGGAGGAACACAGTGGCAGAGGCGACTTTCGGTCTGTAACCTGACACTGAGGCGCAAAGCGTGGGGAGCA
AACAGGATTAGATAACCTGGTAGTCCACGCCGTAAGCAGTGAAGTGTAGAGGGTTTCCGCCCTTATAGTGATG
AAGTTAACGCATTAAGCACCTCCGCTGGGGAGTACGGCCGAAAGCTGAAACTCAAAGGAATTGACGGGGGCCCGCACA
AGCGGTGGAGCATGTGGTTAATTCGAAGCAACGCAAGAACCCTACCAGGCTTGGACATCTCTGAAAACCTTAGAGA
TAGGGCTTCTCCTTGGGAGAAGAGTGACAGGTGGTGCATGGTTGTCGTCAGCTCGTGTCTGAGATGTTGGGTTAAGT
CCCGCAACGAGCGCAACCTTGATTTTAGTTGCCATCATTAAAGTTGGGCATCTAAGGTGACCGCCGGTGACAAACC
AGGAAAGGTGGGATGACGTCAAATCATCATGCCCTTATGACCTGGGCTACACACGTGCTACAATGGACGGTACAAAGA
GCTGCAAGACCGCAGGTGGAGCTAATCATATAAAACCCTTCAGTTCCGGATTGTAGGCTGCAACTCGCCACATGAA
GCTGGAATCGCTAGTAATCCCGGATCAGCATGCCGCGGTGAATACGTTCCGGGCTTGTACACACCGCCGTCACACC
ACGAGTAGTTGTAAACCGGAAAGTCCGGTGGGTAACCTTTTGGAGCCAGCTATCAA
```

Figure 2: Nucleotide sequencing results of TP10-1 bacterial isolates

TP10-1 bacterial isolates have a 99% similarity with *Bacillus cereus* strain GCF112. In the observation of phylogenetic trees, the distance between bacterial isolates of TP10-1 and *Bacillus cereus* strain GCF112 was very close (Fig. 3). This indicates that the bacterial isolate TP10-1 was found to be identical to the *Bacillus cereus* strain GCF112. This is in accordance with Hagström, Pinhassi and Zweifel (2000) whom stating that the isolates with

similar sequences of more than 97% can represent the same species. While the sequence similarity between 93% - 97% can represent the identity of bacteria at the genus level but from different species<sup>13</sup>. This is also consistent with Tamisier et al. (2015) who stated that the recommended threshold is 95% (for genus) and 98.7% (for species) to classify bacterial isolates<sup>14</sup>.

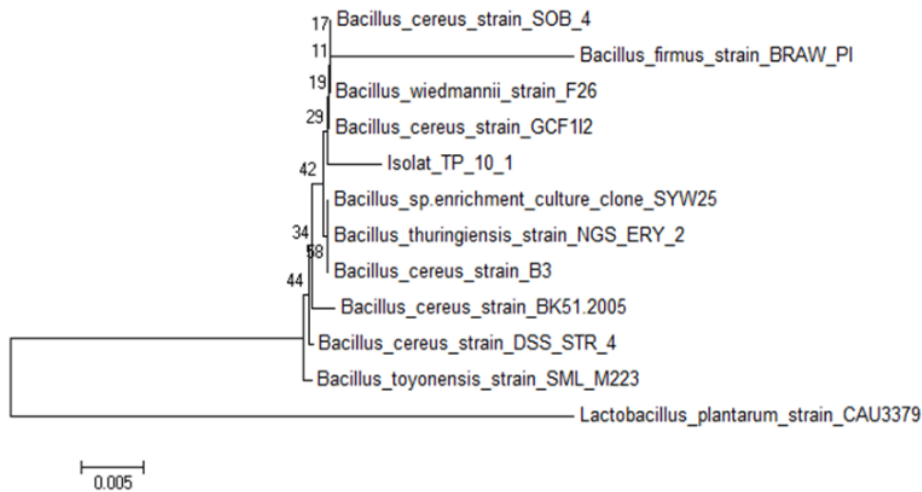


Figure 3: Phylogenetic tree of TP10-1 bacterial isolate

### Extracellular Biosynthesis of Silver Nanoparticles

On visual observation, after the fifth day there was a change in the solution color from being initially yellow to ground brown. The supernatant culture without silver nitrate and 1 mM AgNO<sub>3</sub> solution also observed for color changes and used as controls (Fig. 4). The appearance of brownish color in solution which added with silver nitrate was identified as the formation of silver nanoparticles. This is in accordance with Agrawal and Kulkarni (2017) opinion that the color of the supernatant solution added with 1 mM sterile AgNO<sub>3</sub> will turned brown after incubation<sup>6</sup>. Glishwaral et al. (2008) also stated that supernatant culture that incubated with silver nitrate show color changes from yellow to brown while supernatant culture without silver nitrate and silver nitrate solution (as a control) were observed to have no color changes<sup>5</sup>.

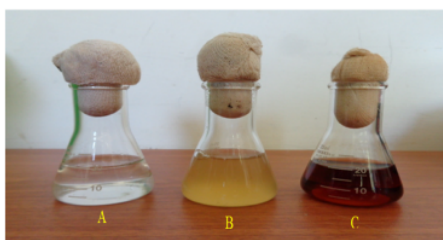


Figure 4: Color change test on bacteria isolates after incubated for 5 days on 37 °C in a dark atmosphere; A. 1 mM AgNO<sub>3</sub> solution, B. Bacterial supernatant C. Bacterial supernatant + 1 mM AgNO<sub>3</sub> solution with color changes in TP 10-1 bacterial isolate.

### Evaluation of the synthesis of silver nanoparticles

The result of UV-Vis spectrophotometer observation was indicated by the formation of the maximum absorption peak of isolate TP10-1 was 414 nm (Fig. 5). This is consistent with the

statement of Sileikaite et al. (2006) stated that silver nanoparticle colloids have typical absorption peaks in visible light with a range of 350 - 530 nm in spectrophotometer analysis<sup>16</sup>.

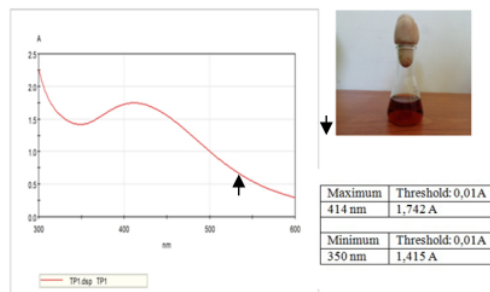


Figure 5: The maximum absorption peak of TP10-1 at 414 nm wavelength

Fourier Transform Infra Red (FTIR) was used to prove the action of TP 10-1 bacterial isolate protein during the process of formation of silver nanoparticles (Fig. 6). FTIR spectra of silver nanoparticles from TP10-1 isolates between wave numbers 400-4000 cm<sup>-1</sup> showed strong peaks in wave numbers 1637.65 cm<sup>-1</sup> and 3329.47 cm<sup>-1</sup>. This is consistent with the opinion of Kong and Yu (2007) whom states that the spectrum region most sensitive to the secondary structural component of protein is the amide I band (1700-1600 cm<sup>-1</sup>) which is almost entirely caused by vibration of C = O stretching connected to the peptide (around 80%). The frequency of amide component I was found to correlate closely with each of the secondary structural elements of the protein<sup>17</sup>. Banker (1992) also states that other amide vibrational bands are very complex depending on the details of the force field, properties of the side chain and hydrogen bonds. Therefore, this method is more practical to used in protein conformation studies<sup>18</sup>.



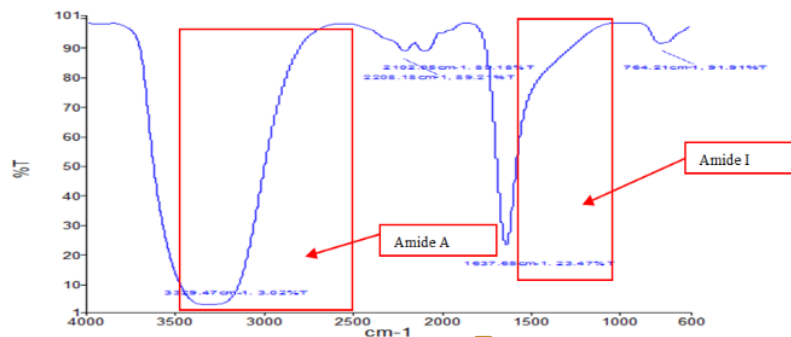


Figure 6: FTIR result of TP10-1 isolate showed the formation of amide peak

The particle size observation of silver nanoparticles was carried out using the imageJ program. This is consistent with Mazolli and Favoni (2012) that stated to evaluate particle size and size distribution, Scanning Electron Microscopy (SEM) and ImageJ

processing programs were used (Fig. 7). The number of analyzed nanoparticles was 5813 of the total 98765 with the average size of the nanoparticles formed was 16.991 nm<sup>19</sup>.

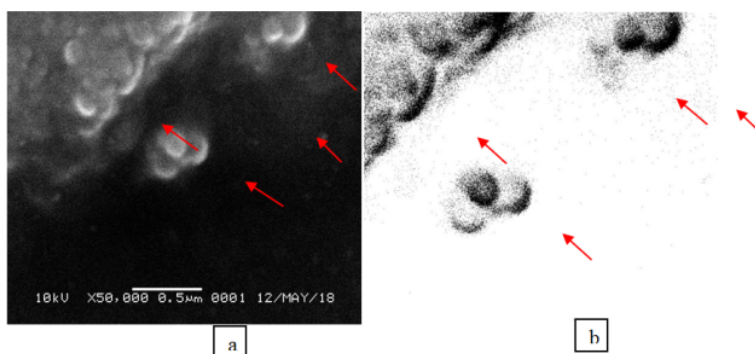


Figure 7: SEM result of TP10-1 bacterial isolate, a. SEM results showed the formation of silver nanoparticles; b. The results of the particle size scanner for silver nanoparticles using ImageJ

The results showed that the TP10-1 bacterial isolate was able to synthesize AgNO<sub>3</sub> solution into silver nanoparticles. This is in accordance with Pugazhenthiran *et al.* (2009) who using *Bacillus sp.* to synthesize silver into silver nanoparticles and obtained a nanoparticle with size of 5-15 nm. Banu *et al.* (2014) was synthesized the nanoparticle from *Bacillus thuringiensis* and obtained nanoparticle with size of 43.52–142.97 nm. El-Shanshoury *et al.* (2011) also synthesized the nanoparticle with *Streptococcus thermophilus* and obtained nanoparticle with size of 28–122 nm<sup>20</sup>. This is in accordance with Srikanth *et al.* (2016) which states that nanoparticle synthesis means making particles with sizes less than 100 nm and at the same time changing their properties or functions<sup>1</sup>.

## CONCLUSION

This study showed the characterization of TP10-1 bacterial isolates that was tested molecularly had 99% similarity with *Bacillus cereus* strain GCF112. This results was confirmed using phylogenetic tree. *Bacillus cereus* strain GCF112 has the potential to synthesize silver nanoparticles. The average particle size formed was 16.991 nm. UV-Vis spectrophotometer observation results were characterized by formation of a maximum absorption peak at 414 nm which is a typical absorption peak for silver nanoparticles. The results of the Fourier Transform Infra

Red (FTIR) proved the interaction of TP 10-1 bacterial isolate protein during the process of forming silver nanoparticles.

## REFERENCES

1. Srikanth S K, Giri D D, Pal D B, Mishra P K, Upadhyay S N. Green synthesis of silver nanoparticles: A review. *Green and Sustainable Chemistry* 2016; 6(1):34-56. <http://doi.org/10.4236/gsc.2016.61004>
2. Ge L, Li Q, Wang M, Ouyang J, Li X, Xing MQM. Nanosilver particles in medical applications: synthesis, performance, and toxicity. *Int. J. Nanomedicine*, 2014; 9(1):2399–2407. <http://doi.org/10.2147/IJN.S55015>
3. Holt J G, Sneath P H A, Mair N S, Sharpe M E. Bergey's manual of systematic bacteriology, Vol 2. Baltimore: Williams and Wilkins, 1986.
4. Djamaan A, Agustien A, Gemeidiya R, Jannah M, Putri A P, Wangi Q A. Isolation and identification of bioplastic producing bacteria from soil at the Top of Marapi Volcano Mountain, West Sumatra, Indonesia. *Der Pharma Chemica*, 2016; 8(11):160-166. <https://www.derpharmachemica.com/archive/dpc-volume-8-issue-11-year-2016.html>
5. Vithiya K, Kumar R, Sen S. *Bacillus sp.* mediated extracellular synthesis of silver nanoparticles. *Int. J. Pharm. Pharm. Sci.* 2014; 6(2):525-527. <https://innovareacademics.in/journal/ijpps/Vol6Suppl2/8505.pdf>

6. Agrawal P N, Kulkarni N S. Biosynthesis of silver nanoparticles from silver resistance bacteria isolated from metal contaminated soil. *Sch. Acad. J. Biosci*, 2017; 5(3):187-191. DOI: 10.21276/sajb.2017.5.3.10
7. Sayuti I, Siregar Y I, Amin B, Agustien A, Djamaan A. Identification of Bacterial Hydrocarbonoclastic in Waste Tanks, Petapahan, Riau, Indonesia, using 16sr RNA, *J. Appl. Microbiol*, 2018; 12(2):671-677.
8. Tamura K, Stecher K, Peterson D, Filipski A, Kumar S. MEGA6: molecular evolutionary genetics analysis version 6.0. *Molecular Biology Evolution* 2013; 30(12): 2725-2729. <https://doi.org/10.1093/molbev/mst197>
9. Shahverdi A R, Minaeian S, Shahverdi H, Jamalifar H, Nohi A A. Rapid synthesis of silver nanoparticles using culture supernatants of Enterobacteria: a novel biological approach. *Process Biochem* 2007; 42:919–923. <http://doi.org/10.1016/j.procbio.2007.02.005>
10. Kalimuthu K, Babu R S, Venkataraman D, Bilal M, Gurunathan, S. Biosynthesis of silver nanocrystals by *Bacillus licheniformis*. *Colloids and Surfaces B: Biointerfaces* 2008; 65:150–153. <http://doi.org/10.1016/j.colsurfb.2008.02.018>
11. Rajeshkumar S, Malarkodi C. In vitro antibacterial activity and mechanism of silver nanoparticles against foodborne pathogens. *Bioinorganic Chemistry and Applications* 2014; Article ID 581890, 1-10. <http://dx.doi.org/10.1155/2014/581890>
12. Ajayi E, Afolayan A. Green synthesis, characterization and biological activities of silver nanoparticles from alkalized *Cymbopogon citratus* Stapf. *Adv. Nat. Sci.: Nanosci. Nanotechnol*, 2017; 8(01),1- 8. <http://doi.org/10.1088/2043-6254/aa5c77>
13. Hagstrom A, Pinhassi J, Zweifel UL. Biogeographical diversity among marine bacterioplankton. *Aquat. Microb. Ecol* 2000; 21:231-244. <http://doi.org/10.3354/ame021231>
14. Tamisier M R, Benamar S, Raoult D, Fournier P E. Cautionary tale of using 16S rRNA gene sequence similarity values in identification of human-associated bacterial species. *IJSEM Papers in Press*. 2015; <http://doi.org/10.1099/ijss.0.000161>
15. Kalishwaralal K, Deepak V, Ramkumar Pandian S, Nellaiah H, Sangiliyandi G. Extracellular biosynthesis of silver nanoparticles by the culture supernatant of *Bacillus licheniformis*. *Elsevier, Materials Letters*, 2008; 62:4411–4413. <https://doi.org/10.1016/j.matlet.2008.06.051>
16. Sileikaite A, Prosycevas I, Puiso J, Juraitis A, Guobiene A. Analysis of silver nanoparticles produced by chemical reduction of silver salt solution. *Materials Science (Medžiagotyra)* 2006;12 (4):287-291. [cited 2018 Apr 16] Available from: <http://citeseerx.ist.psu.edu/viewdoc/download?doi=10.1.1.485.1461&rep=rep1&type=pdf>
17. Kong J, Yu S. Fourier transform infrared spectroscopic analysis of protein secondary structures. *Acta Biochimica et Biophysica Sinica*, 2007;39(8):549–559. PMID: 17687489
18. Banker J. Amide modes and protein conformation. *Biochim Biophys Acta*, 1992; 1120(2):123–143. PMID: 1373323
19. Mazzoli A, Favoni O. Particle size, size distribution and morphological evaluation of airborne dust particles of diverse woods by Scanning Electron Microscopy and image processing program. *Powder Technology* 2012; 225:65–71. <http://doi.org/10.1016/j.powtec.2012.03.033>
20. Singh R, Shedbalkar U U, Wadhvani S A, Chopade B A. Bacteriogenic silver nanoparticles: synthesis, mechanism, and applications. *Appl. Microbiol. Biotechnol.* 2015; 99(11):4579–4593. DOI 10.1007/s00253-015-6622-1. <http://doi.org/10.1007/s00253-015-6622-1>

**Cite this article as:**

Dani Prasetyo et al. Bacterial characterization of silver nanoparticles from Tembapapura soil sample isolate, Papua, Indonesia. *Int. Res. J. Pharm.* 2018;9(10):53-57 <http://dx.doi.org/10.7897/2230-8407.0910225>

Source of support: Nil, Conflict of interest: None Declared

Disclaimer: IRJP is solely owned by Moksha Publishing House - A non-profit publishing house, dedicated to publish quality research, while every effort has been taken to verify the accuracy of the content published in our Journal. IRJP cannot accept any responsibility or liability for the site content and articles published. The views expressed in articles by our contributing authors are not necessarily those of IRJP editor or editorial board members.

# Jurnal\_Bacterial\_Characterization\_of\_silver

---

## ORIGINALITY REPORT

---

18%

SIMILARITY INDEX

%

INTERNET SOURCES

18%

PUBLICATIONS

0%

STUDENT PAPERS

---

## PRIMARY SOURCES

---

- 1** Rizwan Wahab, Shams T. Khan, Javed Ahmad, S.G. Ansari, Javed Musarrat, Abdulaziz A. Al-Khedhairy. "MWCNTs functionalization and immobilization with anti-Brucella antibody; towards the development of a nanosensor", Vacuum, 2017  
Publication 2%

---
- 2** Shaik John Saida, A. Manikandan, Muralidharan Kaliyaperumal, Chidananda Swamy Rumalla et al. "Identification, isolation and characterization of dolutegravir forced degradation products and their cytotoxicity potential", Journal of Pharmaceutical and Biomedical Analysis, 2019  
Publication 2%

---
- 3** Berrak Dumlupinar Altinsoy, Gokce Şeker Karatoprak, Ismail Ocsoy. "Extracellular Directed Ag NPs Formation and Investigation of Their Antimicrobial and Cytotoxic Properties", Saudi Pharmaceutical Journal, 2018  
Publication 1%

---

4

Ke Luo, Samuel Jung, Kyu-Hwan Park, Young-Rok Kim. "Microbial biosynthesis of silver nanoparticles in different culture media", *Journal of Agricultural and Food Chemistry*, 2018

Publication

---

1 %

5

Malcolm Xing, Liangpeng Ge, Meng Wang, Qingtao Li, Xiojian Li, Jun Ouyang. "Nanosilver particles in medical applications: synthesis, performance, and toxicity", *International Journal of Nanomedicine*, 2014

Publication

---

1 %

6

Mahendran Vanaja, Gurusamy Annadurai. "Coleus aromaticus leaf extract mediated synthesis of silver nanoparticles and its bactericidal activity", *Applied Nanoscience*, 2012

Publication

---

1 %

7

Asnani, A, D Ryandini, and Suwandri. "Screening of Marine Actinomycetes from Segara Anakan for Natural Pigment and Hydrolytic Activities", *IOP Conference Series Materials Science and Engineering*, 2016.

Publication

---

1 %

8

Muslim Suardi, Annisa Suri Hamdani, Bertiliyus Ariyati, Rika Sari Lalfari et al. "Utilization of Rice Straw (*Oryza sativa* Linn) Agricultural Waste as Substrate for Poly(3-

1 %



Hydroxybutyrate) Production Using  
*Pseudomonas aeruginosa*", Journal of Pure  
and Applied Microbiology, 2018

Publication

---

9

Kalishwaralal, K.. "Extracellular biosynthesis of silver nanoparticles by the culture supernatant of *Bacillus licheniformis*", Materials Letters, 20081130

Publication

---

1 %

10

M. M. K. Peiris, S. S. N. Fernando, P. M. Jayaweera, N. D. H. Arachchi, T. D. C. P. Guansekara. "Comparison of Antimicrobial Properties of Silver Nanoparticles Synthesized from Selected Bacteria", Indian Journal of Microbiology, 2018

Publication

---

1 %

11

Lateef, A., I. A. Adelere, E. B. Gueguim-Kana, T. B. Asafa, and L. S. Beukes. "Green synthesis of silver nanoparticles using keratinase obtained from a strain of *Bacillus safensis* LAU 13", International Nano Letters, 2014.

Publication

---

1 %

12

Konasur, Sanjay, and Rashmi V. "Green synthesis, characterization and bioactivity of plant-mediated silver nanoparticles using *Decalepis hamiltonii* root extract", IET Nanobiotechnology, 2016.

Publication

---

1 %

13

"Methods of Nanoparticle Biosynthesis for Medical and Commercial Applications", Bio-Nanoparticles, 2015.

Publication

<1 %

14

Rostami, Sima, Reza Salavati, Robin N. Beech, Mitra Sharbatkhori, Zahra Babaei, Sadegh Saedi, and Majid Fasihi Harandi. "Cytochrome c oxidase subunit 1 and 12S ribosomal RNA characterization of *Coenurus cerebralis* from sheep in Iran", *Veterinary Parasitology*, 2013.

Publication

<1 %

15

Yeon Ju Kim, Priyanka Singh, Deok-Chun Yang, Hina Singh, Chao Wang, Mohamed El-Agamy Farh, Kyu Hyon Hwang. "Biosynthesis, characterization, and antimicrobial applications of silver nanoparticles", *International Journal of Nanomedicine*, 2015

Publication

<1 %

16

Sadiya Anjum, Anupama Sharma, Mythili Tummalapalli, Jincy Joy, Surya Bhan, Bhuvanesh Gupta. "A Novel Route for the Preparation of Silver Loaded Polyvinyl Alcohol Nanogels for Wound Care Systems", *International Journal of Polymeric Materials and Polymeric Biomaterials*, 2015

Publication

<1 %

17

Veluchamy Prabhawathi, Ponnurengam Malliappan Sivakumar, Mukesh Doble. "Green

<1 %

## Synthesis of Protein Stabilized Silver Nanoparticles Using Pseudomonas fluorescens, a Marine Bacterium, and Its Biomedical Applications When Coated on Polycaprolactam", Industrial & Engineering Chemistry Research, 2012

Publication

---

18

Balu Chopade, Ghosh, Patil, Ahire, Kitture, Jabgunde, Kale, Pardesi, Cameotra, Bellare, Dhavale. "Synthesis of silver nanoparticles using Dioscorea bulbifera tuber extract and evaluation of its synergistic potential in combination with antimicrobial agents", International Journal of Nanomedicine, 2012

Publication

---

<1 %

19

Irena Maliszewska. "Microbial Synthesis of Metal Nanoparticles", Metal Nanoparticles in Microbiology, 2011

Publication

---

<1 %

20

Mazzoli, Alida, and Giacomo Moriconi. "Particle size, size distribution and morphological evaluation of glass fiber reinforced plastic (GRP) industrial by-product", Micron, 2014.

Publication

---

<1 %

21

Siavash Iravani, Rajender S. Varma. "Bacteria in Heavy Metal Remediation and Nanoparticle

<1 %

Biosynthesis", ACS Sustainable Chemistry & Engineering, 2020

Publication

22

Yugandhar, Pulicherla, Reddla Haribabu, and Nataru Savithramma. "Synthesis, characterization and antimicrobial properties of green-synthesised silver nanoparticles from stem bark extract of *Syzygium alternifolium* (Wt.) Walp.", 3 Biotech, 2015.

Publication

<1 %

23

Zulkarnain Chaidir, Reni Rahmayuni, Akmal Djamaan. "Isolation and Selection of Growth Medium for Microalgae of Lake Biru Sawahlunto West Sumatra and Antibacterial Activity Test", Journal of Pure and Applied Microbiology, 2019

Publication

<1 %

24

A. Janardhanan, T. Roshmi, Rintu T. Varghese, E. V. Soniya, Jyothis Mathew, E. K. Radhakrishnan. "Biosynthesis of silver nanoparticles by a *Bacillus* sp. of marine origin", Materials Science-Poland, 2013

Publication

<1 %

25

Jayanta Kumar Patra, Kwang-Hyun Baek. "Green synthesis of silver chloride nanoparticles using *L. outer peel* extract and investigation of antibacterial, anticandidal,

<1 %

# antioxidant potential ", Green Chemistry Letters and Reviews, 2016

Publication

---

---

Exclude quotes      On

Exclude matches      Off

Exclude bibliography      On